

Evolution of Quantum Criticality in $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$

L Peyker¹, C Gold¹, E-W Scheidt¹, W Scherer¹, J G Donath²,
P Gegenwart³, F Mayr⁴, V Eyert⁵, E Bauer⁶ and H Michor⁶

¹ CPM, Institut für Physik, Universität Augsburg, 86135 Augsburg, Germany

² Max Planck Institute for Chemical Physics of Solids, 01187 Dresden, Germany

³ I. Physikalisches Institut, Georg-August-Universität, 37077 Göttingen, Germany

⁴ EP V, EKM, Institut für Physik, Universität Augsburg, 86135 Augsburg, Germany

⁵ EP VI, EKM, Institut für Physik, Universität Augsburg, 86135 Augsburg, Germany

⁶ Institut für Festkörperphysik, Technische Universität Wien, 1040 Wien, Austria

E-mail: Ernst-Wilhelm.Scheidt@physik.uni-augsburg.de,

Wolfgang.Scherer@physik.uni-augsburg.de

Abstract. Crystal structure, specific heat, thermal expansion, magnetic susceptibility and electrical resistivity studies of the heavy fermion system $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ ($0 \leq x \leq 1$) reveal a continuous tuning of the ground state by Ni/Cu substitution from an effectively fourfold degenerate non-magnetic Kondo ground state of CeNi_9Ge_4 (with pronounced non-Fermi-liquid features) towards a magnetically ordered, effectively twofold degenerate ground state in $\text{CeNi}_8\text{CuGe}_4$ with $T_N = 175 \pm 5$ mK. Quantum critical behavior, $C/T \propto \chi \propto -\ln T$, is observed for $x \cong 0.4$. Hitherto, $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ represents the first system where a substitution-driven quantum phase transition is connected not only with changes of the relative strength of Kondo effect and RKKY interaction, but also with a reduction of the effective crystal field ground state degeneracy.

PACS numbers: 71.27.+a, 71.10.Hf, 75.40.-s

1. Introduction

Since the discovery of non-Fermi-liquid (nFL) behavior in $\text{U}_{0.2}\text{Y}_{0.8}\text{Pd}_3$ characterized by a logarithmic divergence of the Sommerfeld coefficient $\gamma \simeq C/T \propto -\ln(T/T_0)$ [1], the research activity in the field of nFL physics has been very active [2]. Thereby, great attention was devoted to Kondo systems, in particular to those where nFL behavior appears to originate from critical magnetic fluctuations. The latter may emerge near a magnetic phase transition when a subtle balancing of competing interactions shifts a magnetic phase transition towards zero kelvin. In this quantum critical point (QCP) scenario [3, 4, 5], Kondo interactions, favoring a paramagnetic Fermi-liquid ground state, compete with RKKY interactions, favoring a magnetically ordered ground state (for recent reviews, see [6, 7]).

The relative strength of competing Kondo and RKKY interactions, e.g. in Ce- or Yb-intermetallics, can be tuned by parameters such as: (i) pressure [8], (ii) substitutions [9], or (iii) external magnetic fields [10]. Besides these tuning parameters controlling the relative strength of Kondo and RKKY interactions, there is another interesting aspect of heavy fermion quantum criticality which was considered in theoretical studies, but hardly explored experimentally, namely the variation of the effective degeneracy of total angular momentum degrees of freedom. This parameter, abbreviated as *effective spin degeneracy* N , which is the number of crystal field (CF) states with energies up to the magnitude of the Kondo energy, may also drive a system through a QCP. Coleman [11] has shown that the critical value of the Kondo coupling constant above which a spin-compensated ground state is stable tends to zero by $1/N$ as N increases, i.e. systems having a large effective spin degeneracy N are less likely to order magnetically.

In this respect, the heavy fermion CeNi_9Ge_4 represents a suitable model system to study the role of effective spin degeneracy since it displays larger N values than the usual two-fold one in classical nFL systems. Recently, single ion nFL behavior of the specific heat and magnetic susceptibility has been discussed for this system. Here, CeNi_9Ge_4 shows the largest ever recorded value of the electronic specific heat coefficient $\gamma = C/T \approx 5.5 \text{ J K}^{-2} \text{ mol}^{-1}$ at 0.08 K for paramagnetic Kondo-lattices [12, 13]. The dilution of the f -moments via Ce/La substitution, i.e. $\text{Ce}_{1-y}\text{La}_y\text{Ni}_9\text{Ge}_4$, revealed an approximate scaling of the magnetic specific heat contribution and magnetic susceptibility with the cerium ions fraction, thus, indicating that the huge Sommerfeld coefficient γ of CeNi_9Ge_4 is mainly due to Ce single ion effects, i.e. crystal field and Kondo interactions [12]. Another remarkable feature in CeNi_9Ge_4 is its strongly temperature-dependent Sommerfeld-Wilson ratio, $R \propto \chi_0/\gamma$, which is revealed by the distinct different temperature dependencies of specific heat and magnetic susceptibility below 1 K [12].

The origin of this behavior is illuminated by CeNi_9Ge_4 single crystal susceptibility and polycrystal magnetic entropy data revealing a crystal field scheme of Ce^{3+} with a quasi-quartet ground state below 20 K. Thereby, a fourfold effective spin degeneracy of the Ce-ions is based on two doublets with an energy splitting of only 0.5 meV, i.e. of the same order of magnitude as the Kondo energy in this system, which is about 0.3 meV

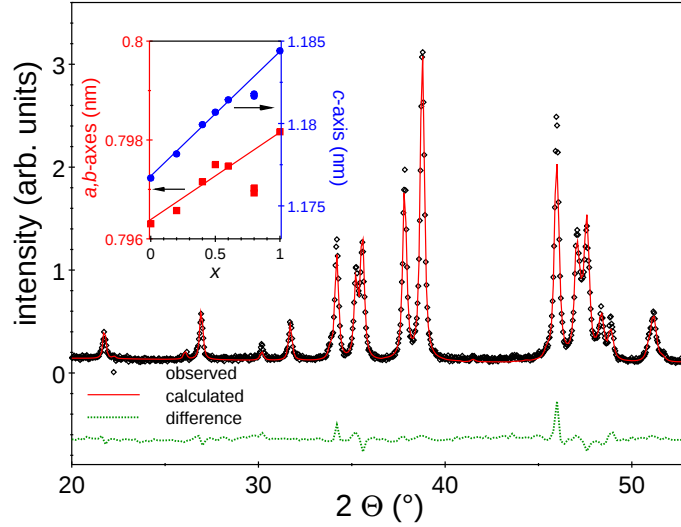


Figure 1. Observed and calculated (Rietveld refinement) x-ray powder diffraction pattern of annealed $\text{CeNi}_8\text{CuGe}_4$. The dotted line displays the difference plot. The insert shows the variation of the lattice parameters of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ with respect to the Cu-concentration x .

[14]. Numerical renormalization group (NRG)-calculations by Anders and Pruschke [15, 16] using the $\text{SU}(4)$ -Anderson impurity model which also accounted for crystal field splitting demonstrated that the Kondo effect in combination with a quasi-quartet CF ground state leads to a $\text{SU}(2)$ to $\text{SU}(4)$ cross-over regime with a significant variation of the Sommerfeld-Wilson ratio as experimentally observed in $\text{Ce}_{1-y}\text{La}_y\text{Ni}_9\text{Ge}_4$.

In this work we study the solid solution $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$, where Ni is gradually replaced by Cu ions up to $x = 1$. This substitution modestly changes the $3d$ -electron number and as a consequence the position of the Fermi level relative to the $\text{Ce-}4f^1$ state. Replacing Ni by Cu is thus expected to influence the Kondo and RKKY interactions. Usually such substitution should lower the Kondo temperature and support the formation of long range magnetic order. The latter effect is also expected as a consequence of an increasing unit cell volume. Even in the absence of any lattice expansion, Ni/Cu substitution reduces the local point symmetry at Ce-sites and thus cancels the quasi-fourfold degeneracy of the CF ground state.

It is important to mention, that isostructural and isoelectronic CeNi_9Si_4 with an almost 4% smaller unit cell volume exhibits distinct Fermi-liquid Kondo lattice behavior with a about one order of magnitude larger Kondo temperature, $T_K \simeq 80 \text{ K}$ [17], compared to CeNi_9Ge_4 . X-ray photoelectron spectroscopy on CeNi_9Si_4 revealed a cerium oxidation state being close to 3+ (in between $\text{Ce}^{3.0+}$ and $\text{Ce}^{3.1+}$) [18], which suggests that cerium in CeNi_9Ge_4 is even close to the trivalent state.

2. Sample preparation and structural characterization

Polycrystalline samples of $CeNi_{9-x}Cu_xGe_4$ and $LaNi_{9-x}Cu_xGe_4$ were prepared by arc-melting of pure elements, Ce: 4N, La: 3N8 (Ames MPC [19]), Ni: 4N5; Cu: 6N; Ge: 5N, under a highly purified argon atmosphere. To obtain the highest possible homogeneity, the samples were flipped over several times and remelted. Subsequently, the samples were annealed in evacuated quartz glass tubes for two weeks at 950°C. Inductively coupled plasma spectroscopy (ICP-OES) studies were carried out and confirmed Ni to Cu ratios in good agreement with the relative amount of the starting materials.

Standard x-ray diffraction techniques using $CuK\alpha$ radiation were performed on carefully prepared sieved powdered samples (grain size 40 μm). $CeNi_9Ge_4$ crystallizes in the tetragonal space group $I4/mcm$ with lattice parameters $a = b = 7.9701(1)\text{\AA}$ and $c = 11.7842(3)\text{\AA}$ (for structural details, see Ref. [12, 13]). From Rietveld analysis (see as one example the $CeNi_8CuGe_4$ pattern in Fig. 1) precise lattice parameters of the solid solutions were determined. The high quality of the refinement ($R_f = 4.14$) is reflected in the difference plot. The analysis indicates that replacement of the Ni ions by Cu leads to a modest volume expansion, increasing linearly up to 0.8% for $x = 1$ (insert of Fig. 1). Lattice parameters of $CeNi_8CuGe_4$ are $a = b = 7.9816(7)\text{\AA}$ and $c = 11.8441(2)\text{\AA}$. Total energies calculations based on the new full-potential augmented spherical wave method [20] suggest some degree of preferential occupation of the three inequivalent Wyckoff positions $16k$, $16l$, and $4d$ by Cu: $E(16k) < E(4d) < E(16l)$. Indeed, the energy increases for Cu placed on $4d$ and $16l$ sites relative to the $16k$ site are about 0.1 eV and 0.2 eV, respectively.

3. Experimental results

3.1. Susceptibility and specific heat

The temperature dependence of the dc magnetic susceptibility was measured between 2 K and 400 K in an applied magnetic field of 0.5 T with a commercial SQUID magnetometer (MPMS7). In the low temperature region ($0.06\text{K} < T < 2.5\text{K}$) these measurements were completed by a self designed ac susceptibility device ($B < 0.3\text{mT}$) installed in a $^3\text{He}/^4\text{He}$ -dilution refrigerator. The absolute values of the low temperature data were obtained by normalizing the ac- χ data to the dc- χ data between 1.8 K and 2.5 K. The specific heat experiments were performed with a commercial equipment (PPMS) between 2 K and 300 K and in a ^3He - ^4He -dilution refrigerator down to a base temperature (BT) of 60 mK using a standard relaxation method [21].

Figure 2 presents the overall susceptibility $\chi(T)$ for various compositions of $CeNi_{9-x}Cu_xGe_4$. Above 100 K all samples follow a simple modified Curie-Weiss type law, $\chi(T) = C/(T - \Theta) + \chi_0$, yielding a paramagnetic Curie-Weiss temperature Θ around -14 K, $\chi_0 \cong 0.9$ memu/mol in reasonable agreement with the Pauli susceptibility of $LaNi_9Ge_4$ and a Curie constant C corresponding to an effective paramagnetic moment of $\cong 2.5\mu_B$, which is in line with the theoretical value of $2.54\mu_B$ for a Ce^{3+} -ion. Starting

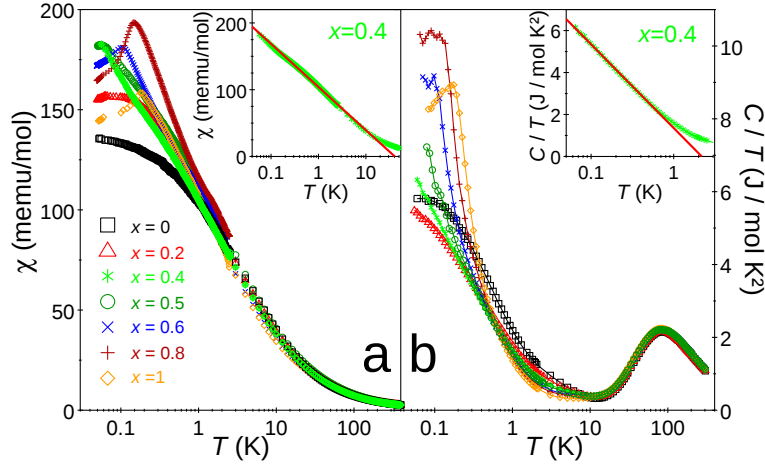


Figure 2. a) The magnetic susceptibility χ and b) the specific heat divided by temperature C/T of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ in semi-logarithmic plots. AFM transitions are evident for $x \geq 0.5$. The inserts show χ and C/T vs. T of $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$: Both solid lines represent logarithmic fits over more than one decade in temperature.

from the parent compound CeNi_9Ge_4 , Ni/Cu substitution initially increases the low temperature susceptibility and reduces the temperature below which it tends to flatten (from $\simeq 1$ K for $x = 0$ to $\simeq 0.2$ K for $x = 0.2$). For $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ we finally observe a $\chi(T) \propto -\ln(T)$ behavior down to the BT of 60 mK (see insert of Fig. 2a) which is indicative of quantum criticality. At even higher Cu concentrations sharp cusps in $\chi(T)$ reveal long range antiferromagnetic (AFM) order. Finally, $\text{CeNi}_8\text{CuGe}_4$ exhibits magnetic ordering below $T_N \approx 175 \pm 5$ mK.

These observations are corroborated by specific heat results shown as C/T vs. T plots for the same compositions of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ in Fig. 2b. In comparison to CeNi_9Ge_4 , the initial substitution of Ni by Cu, $x = 0.2$, reduces the C/T values, and the observed deviation from $C/T \propto -\ln(T)$ behavior (which starts below 250 ± 10 mK for $x = 0$) shifts to 150 ± 10 mK. For $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$, a $C/T \propto -\ln(T)$ divergence of the Sommerfeld coefficient holds over more than one decade in temperature down to the BT of 60 mK (see insert of Fig. 2b). Above $x = 0.4$ magnetic phase transitions are clearly indicated by specific heat anomalies superimposed on a huge background due to heavy electrons with Sommerfeld values C/T exceeding 10 J/mol K^2 for $\text{CeNi}_{8.2}\text{Cu}_{0.8}\text{Ge}_4$.

3.2. Volume thermal expansion

The volume thermal expansion $\alpha(T) = 1/V(\partial V/\partial T)$ is ideally suited to study nFL behavior that results from a QCP, because $\alpha(T) \propto (\partial S/\partial p)$ directly probes the pressure dependence of entropy which is accumulated close to the instability. A theoretical study in terms of a scaling analysis, suggested that the thermal expansion is far more singular than the specific heat $C(T)/T$ at any pressure-sensitive QCP [22].

We obtained $\alpha(T)$ by means of a high-resolution capacitive dilatometer (redesigned after Pott and Schefzyk [23]) attached to a $^3\text{He}/^4\text{He}$ -dilution refrigerator. Measurements

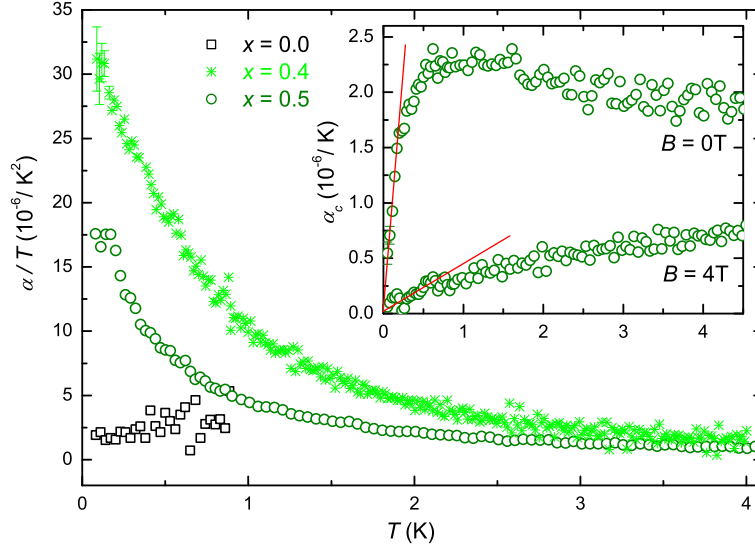


Figure 3. Volume thermal expansion coefficient $\alpha(T)/T$ vs. T of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ for $x = 0, 0.4$, and 0.5 . The errors are indicated by vertical bars. Insert: Linear thermal expansion coefficient $\alpha_c(T)$ of $\text{CeNi}_{8.5}\text{Cu}_{0.5}\text{Ge}_4$ for $B = 0$, and 4 T. Lines represent fits $\alpha_c(T) = a_1 \cdot T$ with $a_1 = 9 \cdot 10^{-6}/\text{K}^2$ and $a_1 = 4 \cdot 10^{-7}/\text{K}^2$ for $B = 0$ T and $B = 4$ T, respectively.

on selected compositions $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ with $x = 0, 0.4$, and 0.5 were carried out between $0.08 \text{ K} < T < 4 \text{ K}$ and in applied magnetic fields up to 4 T . The volume thermal expansion α is given by the sum of the linear thermal expansion coefficients along three perpendicular directions a, b, c , i.e. $\alpha = \alpha_a + \alpha_b + \alpha_c$. Assuming isotropic behavior in our polycrystalline samples, we have obtained the volume expansion as $\alpha = 3 \times \alpha_a$. For the data in a magnetic field, the linear expansion coefficient along the direction of the applied magnetic field has been determined and denoted α_c in the following. This estimate does not take into account that texture may play a role in particular for CeNi_9Ge_4 .

Figure 3 shows the volume thermal expansion $\alpha(T)/T$ vs. T for various concentrations $x = 0, 0.4$, and 0.5 for $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$. It reaches remarkably high values in the order of $10^{-6}/\text{K}^2$, typical for heavy fermion compounds. In agreement with the susceptibility data of the undoped sample, we find $\alpha(T)/T = \text{const}$ for $T < 1 \text{ K}$ indicative for a FL ground state. Substituting Cu for Ni generates singular behavior in $\alpha(T)/T$ which is most pronounced for $x = 0.4$. Further increasing the Cu content causes a saturation of $\alpha(T)/T$ at lowest temperatures $T < 0.2 \text{ K}$ for $x = 0.5$. A suppression of the critical fluctuation is also observed by applying a magnetic field, which is demonstrated for $\text{CeNi}_{8.5}\text{Cu}_{0.5}\text{Ge}_4$ in the insert of Fig. 3. While for $B = 0 \text{ T}$, FL behavior, i.e. $\alpha_c(T)/T = \text{const}$ is found only up to $T \approx 0.2 \text{ K}$, this behavior extends until $T \approx 0.8 \text{ K}$ for $B = 4 \text{ T}$. At the same time, the linear coefficient a_1 of the FL contribution to the thermal expansion coefficient $\alpha_c(T) \simeq a_1 T$ varies by an order of magnitude from $a_1(B = 0 \text{ T}) = 9 \cdot 10^{-6}/\text{K}^2$ to $a_1(B = 4 \text{ T}) = 4 \cdot 10^{-7}/\text{K}^2$, indicating that α_c/T is strongly suppressed in magnetic field. Such behavior is found in many

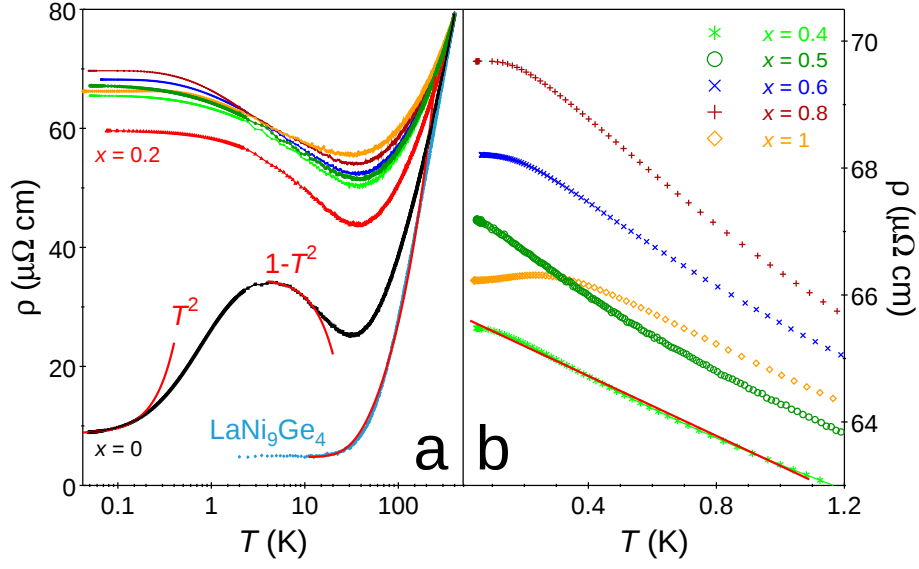


Figure 4. a) A semi-logarithmic plot of the electrical resistivity $\rho(T)$ of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ normalized at 300 K to that of LaNi_9Ge_4 which was measured with the Vander-Pauw method. The solid lines depict T^2 -fits for CeNi_9Ge_4 and a Bloch-Grüneisen fit for LaNi_9Ge_4 . CeNi_9Ge_4 exhibits Kondo-lattice behavior. b) In a linear plot of ρ vs. T the development of a long range ordered AFM phase transition is observed for $x \geq 0.5$, while the resistivity for $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ is linear down to 80 mK (solid line).

quantum critical systems [24, 25].

3.3. Electrical resistivity

The concentration dependent crossover from Kondo lattice behavior with unusual single-ion nFL features of the specific heat and magnetic susceptibility in CeNi_9Ge_4 to long range magnetic order in $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ is also revealed by resistivity measurements (Fig. 4a). While the LaNi_9Ge_4 reference sample exhibits a normal metallic Bloch-Grüneisen behavior with a very low residual resistivity of $5 \mu\Omega \text{ cm}$, CeNi_9Ge_4 seems to represent a classical Kondo lattice, with a residual resistivity $\rho_0 \simeq 9 \mu\Omega \text{ cm}$ of a very pure sample. After passing a minimum around 30 K and a logarithmic increase, the resistivity follows a $1 - T^2$ law as it is known for Kondo systems. At lower temperatures the resistivity passes through a maximum at a temperature $T^* \simeq 3 \text{ K}$ and follows a T^2 -behavior below the Fermi-liquid temperature $T_{\text{FL}} \simeq 160 \text{ mK}$. While T_{FL} is close to the temperature where C/T deviates from the $C/T \propto -\ln T$ trend, T^* coincides approximately with the temperature below which the susceptibility of CeNi_9Ge_4 deviates from the $\chi \propto -\ln T$ behavior of $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$.

For the Cu-substituted samples the resistivity passes through a Kondo minimum around 30 K, followed by a logarithmic increase at lower temperatures. For $x = 0.4$ the resistivity increases linearly below 1 K indicating nFL behavior (Fig. 4b). This particular behavior was observed for so called disordered Kondo-systems [26, 27]. For

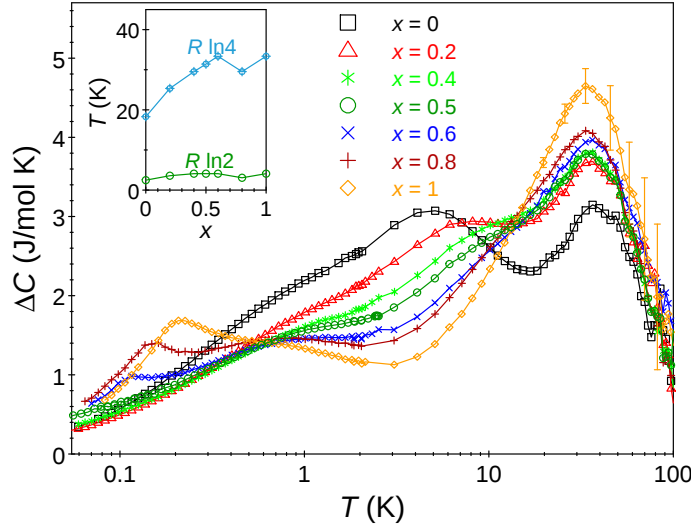


Figure 5. Temperature dependency of the magnetic specific heat ΔC of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ in semi-logarithmic representation. The errors are indicated by vertical bars exemplary for $\text{CeNi}_8\text{CuGe}_4$. The resulting temperatures where the entropy reaches $R\ln 2$ and $R\ln 4$ with respect to the Cu concentration x are plotted in the insert.

$x \geq 0.5$ the resistivity exhibits a bending at lower T for some samples and a maximum for $\text{CeNi}_8\text{CuGe}_4$ denoting long range magnetic order. This is in line with the evolution of the AFM transition observed in C/T - and χ -measurements.

4. Discussion

4.1. Analysis of the high temperature specific heat

To track the mechanism driving the system from Kondo lattice behavior with unusual nFI features towards RKKY antiferromagnetism, we extract the magnetic contribution of the specific heat by subtracting the total specific heat of the system $\text{LaNi}_{9-x}\text{Cu}_x\text{Ge}_4$ with unoccupied $4f$ states. We therefore synthesized the $4f^0$ reference compounds LaNi_9Ge_4 and $\text{LaNi}_8\text{CuGe}_4$ and interpolated the total specific heat data of the corresponding La-sample for each respective composition linearly.

The magnetic contribution to the specific heat ΔC of all $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ samples is depicted in Fig. 5. The reliability of ΔC is indicated by vertical error bars which become larger at high temperature because of the relatively large phonon background. For CeNi_9Ge_4 , two pronounced maxima occur around 5 K and 35 K. The former is associated with the effectively fourfold degenerate Kondo lattice ground state which is composed by $\Gamma_7^{(1)}$ and $\Gamma_7^{(2)}$ CF doublets with an energy splitting of comparable magnitude as the Kondo energy [15, 16]. Thus, a broad Kondo-like contribution rather than a CF Schottky anomaly becomes visible. The second, Schottky-like maximum at about 35 K is associated with a third CF doublet (Γ_6). With increasing Cu-concentration this specific heat maximum gains in height, but remains roughly at the same position near 35 K. In

contrast, the lower Kondo-like maximum decreases and broadens. At a Cu concentration of $x = 0.4$ a clear separation is observed dividing the broad hump into a low lying anomaly around 0.8 K, while the upper anomaly is shifted towards higher temperature. Finally, for $x = 1$, the latter merges with the Schottky contribution centered at about 35 K. The appearance of two separated maxima upon Ni/Cu-substitution, originating from the initially single but broad low temperature maximum of pure CeNi_9Ge_4 , indicates a reduction of the effective spin degeneracy of the Ce-ions from fourfold in the case of CeNi_9Ge_4 to a twofold one for $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$.

The evolution of the temperature dependent magnetic entropy gain, $\Delta S(T)$, further supports a change of energy scales. The insert in Fig. 5 shows those temperatures where the entropy approaches $R \ln 2$ and $R \ln 4$ in dependency of the Cu concentration. Both values, $T(S = R \ln 2)$ and $T(S = R \ln 4)$, increase significantly from CeNi_9Ge_4 to $\text{CeNi}_{8.4}\text{Cu}_{0.6}\text{Ge}_4$, thus, indicating a distinct change of the CF scheme and/or Kondo energy scale. An increase of the Kondo energy may be anticipated from the observed increase of $T(S = R \ln 2)$, but this trend contradicts the expectation of the change in electron number and unit cell volume, namely, a reduction of T_K when proceeding from CeNi_9Ge_4 to $\text{CeNi}_8\text{CuGe}_4$.

4.2. Analysis of the low temperature specific heat

To obtain a more reliable estimate for the trend of the Kondo energies in $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ we utilized the resonant-level model by Schotte and Schotte [28] in combination with a molecular field approach to account for long-range magnetic order [29, 30].

For a spin 1/2 system the magnetic contribution of the specific heat $C_{mag}(T)$ follows in this model from:

$$C_{mag} = 2k_B R e \left\{ \frac{z}{T} \left[1 - \left(\frac{z}{T} - \frac{\partial z}{\partial T} \right) \psi' \left(\frac{1}{2} - \frac{z}{T} \right) \right] \right\}, \quad (1)$$

where $z = T_K + iE(T)/2\pi k_B$, with T_K the Kondo temperature and E the Zeeman energy, and ψ' is the derivative of the digamma function. By factoring the mean field theory into the resonant-level model, E gets temperature dependent with

$$E(T) = g\mu_B \lambda M(T) = J \frac{M(T)}{g\mu_B}. \quad (2)$$

Table 1. Exchange interaction J , the Kondo temperature T_K as calculated from the resonant-level model by Schotte and Schotte [28] including the molecular field approximation and the experimentally observed Néel temperature T_N .

x	J (K)	T_K (K)	T_N (mK)
0.5	< 3.9	2.5	55 ± 10
0.6	3.6	2.2	100 ± 5
0.8	2.9	1.7	135 ± 5
1.0	2.3	1.3	175 ± 5

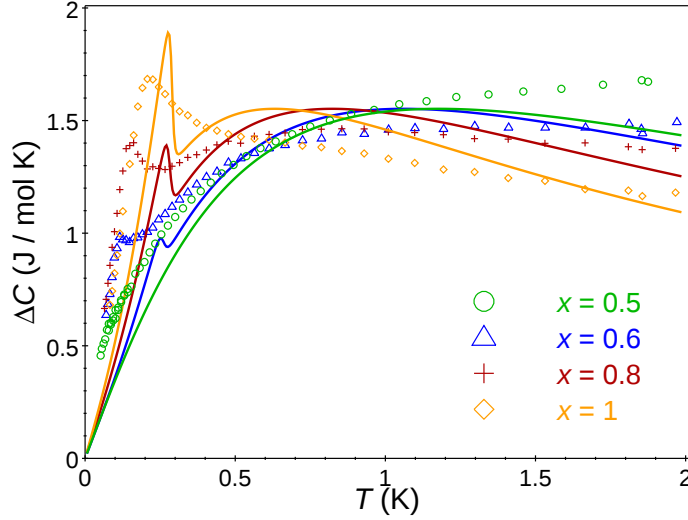


Figure 6. Magnetic contribution to the temperature-dependent specific heat ΔC of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ plotted versus T below 2 K. The solid lines are fits according to the resonant-level model of Schotte and Schotte [28] (see text).

Here g is the Landé-factor (for Ce^{3+} : $g = 6/7$), λ is the molecular-field constant, J describes the s - f exchange interaction and $M(T)$ is the simple magnetization for a two level system. Since the levels are broadened by the Kondo effect the simple Brillouin function becomes modified and $M(T)$ reads:

$$M(T) = \frac{g\mu_B}{\pi} \text{Im} \left[\psi \left(\frac{1}{2} + \frac{T_K + iE(T)}{2\pi k_B T} \right) \right] \quad (3)$$

Finally, while Eq. (2) and Eq. (3) are implicit equations for $E(T)$ and $M(T)$, respectively, we have to calculate the specific heat (Eq. (1)) numerically.

Model calculations for specific heat data were done for all samples with $x \geq 0.5$. In this composition range, $T(S = R \ln 2)$ and $T(S = R \ln 4)$ are roughly constant at values almost twice as large as for CeNi_9Ge_4 (insert of Fig. 5).

The results are plotted in Fig. 6. This simple molecular field model plus the Kondo effect based on a doublet ground state, of course, does not account for any kind of short range magnetic correlations or fluctuations. It therefore fails to fit the experimental data over an extended temperature range. Nevertheless, it qualitatively reproduces the evolution of the magnetic specific heat anomalies and Kondo contributions of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ for $x > 0.5$. The exchange interactions J and the Kondo temperatures T_K obtained from the resonant-level model are recorded in Tab. 1. In addition, T_K is depicted in a magnetic phase diagram of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ (see Sec. 4.4). A linear extrapolation of the T_K values above $x = 0.5$ suggests a $T_K = 3.5$ K for CeNi_9Ge_4 , which is in line with T_K revealed by the quasi-elastic line width observed by cold neutron scattering [14]. The substantial reduction of T_K with increasing Cu concentration is in accordance with the usual trend observed in case of Ni/Cu substitution in other Cerium heavy fermion systems [31]. In addition, the drop of T_K combined with the lowering of the exchange interaction parameter J is in accordance with the Doniach picture [32].

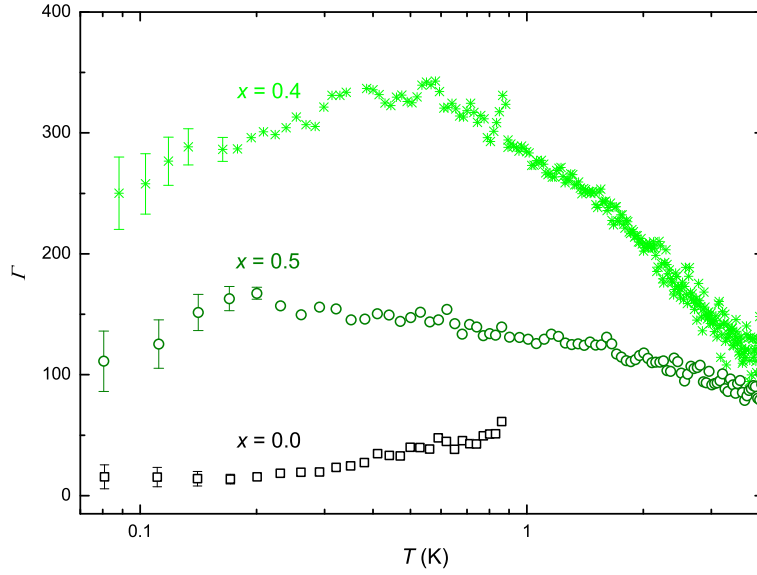


Figure 7. Temperature dependency of the dimensionless Grüneisen ratio $\Gamma(T) = V_m/\kappa_T \cdot \alpha(T)/C(T)$ of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ in semi-logarithmic representation ($V_m = 7.485 \cdot 10^{-28} \text{ m}^3$, $\kappa_T = 1 \cdot 10^{-11} \text{ Pa}^{-1}$, see text for details).

Therefore, the change of the magnetic entropy gain observed from $x = 0$ to $x = 0.5$ is thus attributed to CF effects with a reduction of the effective spin degeneracy of Ce-ions from fourfold in case of CeNi_9Ge_4 to a twofold one for $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$.

4.3. Thermal expansion and Grüneisen ratio

To analyze the nature of the QCP indicated by the thermodynamic data of $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ we calculate the dimensionless Grüneisen ratio $\Gamma(T) = (V_m/\kappa_T) \cdot \alpha(T)/C(T)$ displayed in Fig. 7 for $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ with $x = 0, 0.4$, and 0.5 . In this calculation of $\Gamma(T)$, the molar volume is $V_m = 7.485 \cdot 10^{-28} \text{ m}^3$ and the isothermal compressibility is assumed to be $\kappa_T = 1 \cdot 10^{-11} \text{ Pa}^{-1}$ which is a typical value for heavy fermion systems. The temperature independent Grüneisen ratio of CeNi_9Ge_4 [$\Gamma(T) = \text{const.}$] below 200 mK and the enhanced values of Γ compared to usual metals characterize CeNi_9Ge_4 as Kondo lattice system [33]. In contrast to the latter system, both $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ and $\text{CeNi}_{8.5}\text{Cu}_{0.5}\text{Ge}_4$ exhibit an order of magnitude higher Γ values which are typical for heavy fermion systems close to a magnetic instability [24, 34, 35]. For the antiferromagnetic system $\text{CeNi}_{8.5}\text{Cu}_{0.5}\text{Ge}_4$, a negative Grüneisen ratio is expected below the Neel-temperature ($T_N = 55 \text{ mK}$). The decrease of $\Gamma(T)$ below 0.2 K may indicate short-range order above T_N . In particular for $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ the high Γ values [$\Gamma(0.35 \text{ K}) = 340$] and the strong temperature dependence of $\Gamma(T)$ above 0.35 K are quite different to the parent compound CeNi_9Ge_4 and suggest the vicinity to a QCP. Below 0.35 K, $\Gamma(T)$ saturates and passes a broad maximum, indicating that quantum critical behavior, i.e. the divergence of $\Gamma(T \rightarrow 0)$ suggested by Zhu et al. [22], is vanishing at very low temperatures. This could be explained by assuming

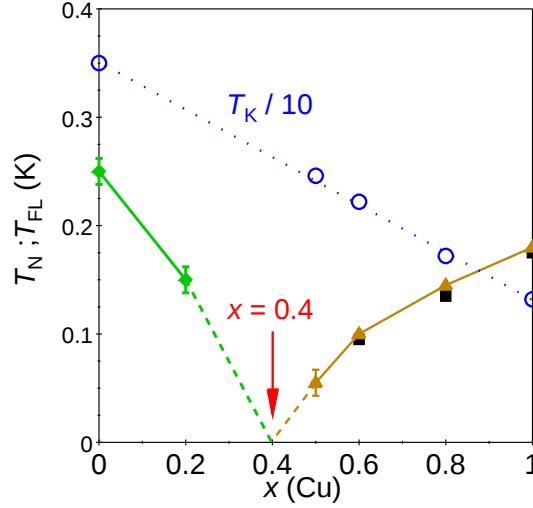


Figure 8. Magnetic phase diagram of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$: The squares and triangles depict T_N as extracted from the C/T and χ data, respectively, while the diamonds represent T_{FL} also derived from C/T . The Kondo temperature T_K (circles) is deduced from the resonant-level model of Schotte and Schotte [28] (see Fig. 6 and Tab. 1).

that either the $x = 0.4$ system is located somewhat away from the QCP or that the quantum phase transition is slightly rounded by disorder in line with the results of the electrical resistivity. Above 0.35 K the Grüneisen ratio follows within the experimental resolution a logarithmic dependence, which clearly deviates from the scaling prediction for a standard QCP by Zhu et al. [22]. We speculate, that the reduction of the effective crystal field ground state degeneracy near the quantum phase transition may modify quantum criticality in our system.

4.4. Evolution of quantum criticality and crystal field

The phase diagram of $\text{CeNi}_{9-x}\text{Cu}_x\text{Ge}_4$ illustrates the presence of a quantum phase transition near $x = 0.4$ (Fig. 8). The FL temperature T_{FL} is estimated from the deviation from the logarithmic temperature behavior of the specific heat divided by temperature C/T in the purely Kondo region. In addition, the Néel temperature T_N is derived from the sharp curvature of the C/T and susceptibility χ data found in the AFM region. Although the T_{FL} values tend to zero around $x \approx 0.4$, the fourfold degenerated ground state of CeNi_9Ge_4 noticeable splits into two doublets indicating that samples with $x > 0.4$ exhibit long range antiferromagnetic order. The C/T and χ values display logarithmic temperature dependence over more than one decade in temperature to the BT of 60 mK at a critical concentration of $x = 0.4$, while the resistivity ρ displays a linear T -dependence and the thermal expansion coefficient α/T diverges. These results signify the presence of a heavy-fermion QCP. In $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$, the nFL state develops from a crossover between a Kondo state ($x \leq 0.4$), where T_{FL} tends to zero, to an antiferromagnetic coherent state ($x \geq 0.4$) starting from $T_N = 0$ K at $x = 0.4$.

To elucidate the change of the CF scheme in the solid solution from CeNi_9Ge_4 with

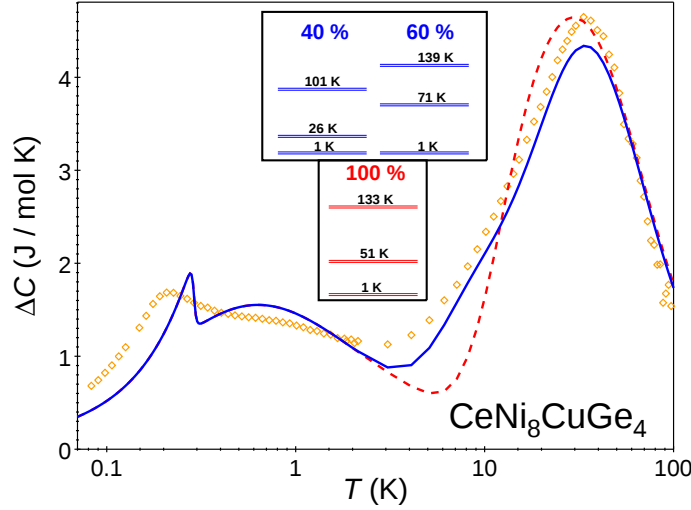


Figure 9. The magnetic contribution of the specific heat ΔC of $\text{CeNi}_8\text{CuGe}_4$ is plotted from 70 mK to 100 K. The dashed and solid lines are theoretical adjustments to the data taking into account the resonant-level model [28] and two Schottky terms originating from only one (dashed line) or two (solid line) different CF environments, respectively (see text).

quasi-fourfold ground state [12, 14] to $\text{CeNi}_8\text{CuGe}_4$ we have quantitatively analyzed the magnetic contribution of the specific heat ΔC of $\text{CeNi}_8\text{CuGe}_4$ by model calculations which combine specific CF schemes with an energy split ground state doublet as considered above in the resonant level model for $\text{CeNi}_8\text{CuGe}_4$ with $J = 2.3$ K and $T_K = 1.3$ K (see Tab 1). In Fig. 9 two model cases considering different crystal field tuning mechanisms are displayed. The first one is based on a unique crystal field environment for each Cerium atom. Here the CF splitting of the $J = 5/2$ state, $\Delta_1 = 51$ K is significantly larger than $\Delta_1 \sim 6$ K of the undoped CeNi_9Ge_4 , whereas $\Delta_2 = 133$ K is of similar magnitude (see dashed line in Fig. 9). The second model scenario considers two or more different CF environments arising from a stochastic occupation of the Cu atoms on the Ni1 site (Wyckoff position $16k$; Sec. 2). For example, the solid line in Fig. 9 represents a model calculation based on two weighted CF-schemes, which consist of 40% of $\Delta_1 = 26$ K, $\Delta_2 = 101$ K and 60% of $\Delta_1 = 71$ K, $\Delta_2 = 139$ K. This second model is more consistent with the experimental specific heat data of $\text{CeNi}_8\text{CuGe}_4$ than the model with a unique CF scheme. In addition, preliminary inelastic neutron scattering (INS) studies indicate a more complex scheme of CF transitions, thus, supporting the model with more than one CF environments of Cerium. Therefore, the nFL behavior of $\text{CeNi}_{8.6}\text{Cu}_{0.4}\text{Ge}_4$ is attributed to a QCP scenario resulting from both a change in the CF environment and a non-unique CF scheme. To clarify the role of chemical disorder upon the CF scheme in these samples, INS studies are in progress.

5. Summary

In conclusion, in the system $CeNi_{9-x}Cu_xGe_4$ ($0 \leq x \leq 1$) the change from an effectively fourfold degenerate to a twofold degenerate ground state is accompanied by a quantum phase transition near $CeNi_{8.6}Cu_{0.4}Ge_4$ that separates $CeNi_9Ge_4$, a Kondo lattice with unusual nFl features, from the antiferromagnetically ordered state for $x \geq 0.4$. In this solid solution Ni/Cu substitution crucially alters the local CF environment of the Ce-ions. This leads to a quantum phase transition, which is not only driven by the competition between Kondo effect and RKKY interaction, but also by a reduction of the effective crystal field ground state degeneracy.

6. Acknowledgments

This work was supported by the Deutsche Forschungsgemeinschaft (DFG) under Contract No. SCHE487/7-1, the research unit 960 "Quantum phase transitions" and by the COST P16 ECOM project of the European Union.

References

- [1] Seaman C L, Maple M B, Lee B W, Ghamaty S, Torikachvili M S, Kang J-S, Liu L Z, Allen J W, and Cox L D 1991 *Phys. Rev. Lett.* **67** 2882 (1991).
- [2] Stewart G R 2001 *Rev. Mod. Phys.* **73** 797; Stewart G R 2006 *Rev. Mod. Phys.* **78** 743
- [3] Hertz J A 1976 *Phys. Rev. B* **14** 1165
- [4] Millis A J 1993 *Phys. Rev. B* **48** 7183
- [5] Moriya T and Takimoto T 1995 *J. Phys. Soc. Jpn.* **64** 960
- [6] von Löhneysen H, Rosch A, Vojta M and Wölfle P 2007 *Rev. Mod. Phys.* **79** 1015
- [7] Gegenwart P, Si Q and Steglich F 2008 *nature physics* **4** 186
- [8] Bogenberger B and von Löhneysen H 1995 *Phys. Rev. Lett.* **74** 1016
- [9] Andracka B and Stewart G R 1993 *Phys. Rev. B* **47** 3208
- [10] Heuser K, Scheidt E-W, Schreiner T and Stewart G R 1998 *Phys. Rev. B* **57** R4198
- [11] Coleman P 1983 *Phys. Rev. B* **28** 5255
- [12] Killer U, Scheidt E-W, Eickerling G, Michor H, Sereni J, Pruschke T and Kehrein S, 2004 *Phys. Rev. Lett.* **93** 216404
- [13] Michor H, Bauer E, Dusek C, Hilscher G, Rogl P, Chevalier B, Etourneau J, Giester G, Killer U and Scheidt E-W 2004 *J. Magn. Magn. Mater.* **272-276** 227
- [14] Michor H, Adroja D T, Bauer E, Bewley R, Dobozanov D, Hillier A D, Hilscher G, Killer U, Koza M, Manalo S, Manuel P, Reissner M, Rogl P, Rotter M and Scheidt E-W 2006 *Physica B* **378-380** 640
- [15] Scheidt E-W, Mayr F, Killer U, Scherer W, Michor H, Bauer E, Kehrein S, Pruschke T and Anders F 2006 *Physica B* **378-380** 154
- [16] Anders F and Pruschke T 2006 *Phys. Rev. Lett.* **96** 086404
- [17] Michor H, Berger S, El-Hagary M, Paul C, Bauer E, Hilscher G, Rogl P and Giester G 2003 *Phys. Rev. B* **67** 224428
- [18] Wang X, Michor H and Grioni M 2007 *Phys. Rev. B* **75** 035127
- [19] Materials Preparation Center, Ames Laboratory, US DOE Basic Energy Sciences, Ames, IA, USA, available from: <www.mpc.ameslab.gov>.
- [20] Eyert V 2007 *The Augmented Spherical Wave Method – A Comprehensive Treatment (Lect. Notes Phys. vol 719)* (Springer, Berlin Heidelberg); Eyert V *J. Comp. Chem.* in press

- [21] Bachmann R, DiSalvo F J, Geballe T H, Greene R L, Howard R E, King C N, Kirsch H C, Lee K N, Schwall R E, Thomas U-H and Zubeck R B 1972 *Rev. Sci. Instrum.* **43** 205
- [22] Zhu L, Garst M, Rosch A, Si Q 2003 *Phys. Rev. Lett.* **91** 066404
- [23] Pott R and Schefzyk R 1983 *J. Phys. Sci. Inst.* **16** 444
- [24] K  chler R, Oeschler N, Gegenwart P, Cichorek T, Neumaier K, Tegus O, Geibel C, Mydosh J A, Steglich F, Zhu L, Si Q 2003 *Phys. Rev. Lett.* **91** 066405
- [25] Donath J G, Steglich F, Bauer E D, Sarrao J L, Gegenwart P 2008 *Phys. Rev. Lett.* **100** 136401
- [26] Bernal O, MacLaughlin D E, Lukefahr H G and Andraka B 1995 *Phys. Rev. Lett.* **75** 2023
- [27] Miranda E, Dobrosavljevic V and Kotliar G, 1997 *Phys. Rev. Lett.* **78** 290
- [28] Schotte K D and Schotte U 1975 *Phys. Lett. A* **55** 38
- [29] Bredl C D, Steglich F and Schotte K D 1978 *Z. Phys. B* **29** 327
- [30] Griбанov A, Tursina A, Murashova E, Seropegin Y, Bauer E, Kaldarar H, Lackner R, Michor H, Royanian E, Reissner M and Rogl P 2006 *J. Phys.: Condens. Matter* **18** 9593
- [31] Nieuwenhuys G J 1995 *Handbook of Magnetic Materials* ed. K H J Buschow (Amsterdam: North-Holland) chapter 1, p 1
- [32] Doniach S, 1977 *Physica B & C* **91** 231
- [33] Takke R, Niksch M, Assmus W, L  thi B, Pott R, Schefzyk R and Wohlleben D K, 1981 *J. Phys.: Condens. Matter* **44** 33
- [34] Kambe S, Flouquet J, Lejey P, Hean P, de Visser A 1997 *J. Phys.: Condens. Matter* **9** 4917
- [35] K  chler R, Gegenwart P, Heuser K, Scheidt E-W, Stewart G R, Steglich F 2004 *Phys. Rev. Lett.* **93** 096402